

## **EXPERIMENTAL STUDY ON THE INFLUENCE OF LARGE LONGITUDINAL REBAR RATIOS ON THE CRACKING CHARACTERISTICS OF R/C ELEMENTS**

**Theodoros A. Chrysanidis<sup>1\*</sup>**

<sup>1</sup> Aristotle University of Thessaloniki  
P.C. 54124, Thessaloniki, Greece  
[theodoros\\_gr@yahoo.com](mailto:theodoros_gr@yahoo.com)

---

### **Abstract**

*Cracking phenomenon in reinforced concrete members has troubled researchers and engineers worldwide due to the many mechanical parameters affecting this phenomenon. One such mechanical parameter is the longitudinal reinforcement ratio used for the detailing of structural components in reinforced concrete structures. Although, the percentage of rebar content has been studied, it is the first time that cracking behaviour is studied using varying large ratios of rebars strained under a uniaxial tensile loading till a high degree of elongation found only at buildings sustained severe earthquake actions. This research is experimental. Four test specimens in the form of R/C ties are used and strained using a monotonic uniaxial tensile loading simulating the tensile type of loading during the first cycle of dynamic seismic action. All specimens are strained till an elongation degree equal to 30%. The ratios used for the reinforcement of column specimens take values equal to 5.47%, 6.03%, 7.15% and 8.21%. Significant conclusions are reached concerning cracking behaviour for different longitudinal ratios, e.g., number of cracks, crack width, etc.*

**Keywords:** Large Longitudinal Ratio, Cracking, Elements, Width

---

## 1 INTRODUCTION

Several international researchers have explored the phenomenon of cracking in reinforced concrete structures [1]–[7]. Although most of the given structures are typically reinforced in two directions, most studies carried out worldwide to investigate the behaviour of cracking have involved uniaxially strained reinforced concrete members with reinforcement in only one direction. To date there is not yet a widely established and accepted methodology for predicting cracking characteristics, e.g. crack widths and spacings between cracks [8]–[11]. In addition, most of the existing research conducted has been strictly limited to the state of the stabilized crack pattern only and does not involve cracking behaviour and crack characteristics deep in the yield region [12], [13]. It has to be noted the fact that cracking can occur in several situations, e.g., transverse buckling of R/C structural walls or retaining walls under cyclic seismic loading [14]–[17], phenomena appearing due to soil-structure interaction [18]–[22], etc. The cost of repairing the cracking and the possible resulting corrosion to the reinforcement bars is something which needs to be taken into account by consulting engineers, too [23], [24]. Furthermore, cracking can reduce the load-bearing capacity of R/C members [11], [25], [26].

In the framework of the current study, an experimental program has been conducted involving reinforced concrete members detailed in two directions using longitudinal rebars and transverse reinforcement in the form of ties. This is a common construction practice used, in at least, the vast majority of concrete structures. As per the results outlined within this work, cracking behaviour and the crack characteristics are discussed. Afterwards, the aforementioned experimental results are analysed and the results of the analysis given in the form of diagrams are discussed. Useful conclusions concerning cracking for different longitudinal reinforcement ratios are derived.

## 2 EXPERIMENTAL PROGRAM

The current experimental program consists of four test specimens. The thickness of each specimen is 7.5 cm and the length of the cross-section is 15 cm. The ratio between the length and the thickness of the cross-sectional area is equal to 2, which is a typical ratio for constructing reinforced concrete columns. The total height of the test specimen is equal to 90 cm. Each of the four specimens is subjected to a uniaxial central tensile loading. The main test element is between the metal plates and its height is 64 cm (Figure 1). A universal testing machine was used to apply the load. The nominal degree of elongation for all specimens is 30.00%. Figure 2 displays the experimental configuration for imposing the central tensile load. The rate of loading was slow, of the order of 4 mm/min, so no result was affected by the influence of the strain rate [27]–[31].

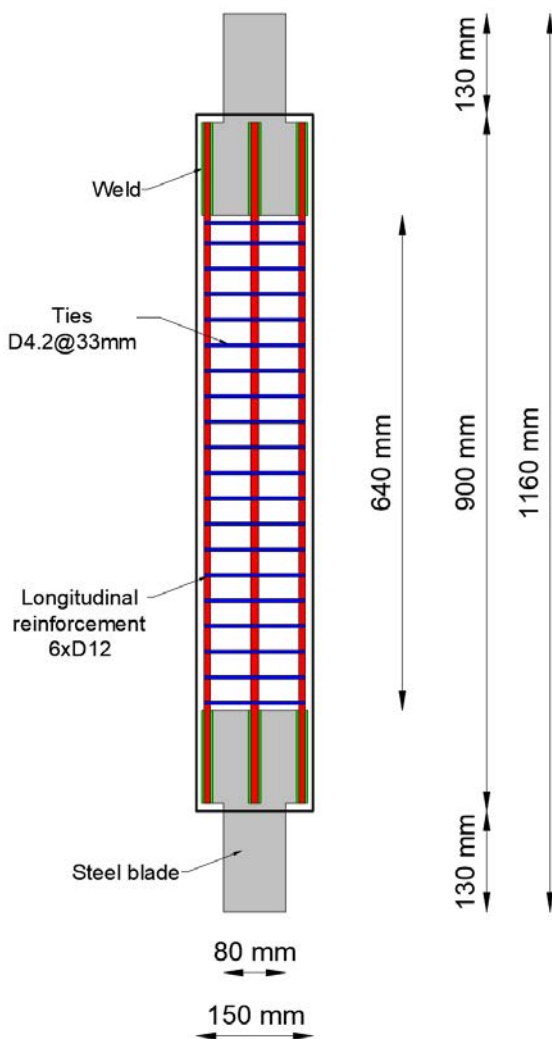


Figure 1: Vertical reinforcement layout for specimen reinforced with 6xD12.



Figure 2: Loading test configuration.

Table 1 shows the geometrical and detailing characteristics of all four specimens. All four segments tested here have been worked on in two directions through deformed bars in terms of reinforcement. The reinforcement for all four prisms is higher than the biggest rebar ratio allowed by codes due to research reasons. The construction scale used to simulate typical columns or typical confined boundaries was equal to 1:3, commonly used for research purposes worldwide [32], [33].

The degree of elongation is equal to 30.00% for all specimens. The transverse reinforcement consists of transverse ties placed along the height of the prism. The centre-to-centre distance between two ties is about 3.3 cm and the diameter of each tie is 4.2 mm. The only variable differentiating specimens from each other is the longitudinal reinforcement ratio. The rebar percentage takes values equal to 5.47%, 6.03%, 7.15% and 8.21%. It is well known that in real constructions, longitudinal ratios up to 4.00% are allowed [34]–[38]. However, there is also, of course, the research interest itself, in examining what happens to cracking characteristics and their behaviour when such rebar percentages are used.

Table 1: Properties of prism specimens

N/A	Specimen name	Length (cm)	Thickness (cm)	Effective height (cm)	Longitudinal reinforcement	Longitudinal reinforcement ratio [ $\rho_l$ ] (%)	Transverse reinforcement	Nominal tensile strain (‰)
1	C-5.47-4Ø14	15	7.5	64	4xD14	5.47	D4.2@33 mm	30.00
2	C-6.03-6Ø12	15	7.5	64	6xD12	6.03	D4.2@33 mm	30.00
3	C-7.15-4Ø16	15	7.5	64	4xD16	7.15	D4.2@33 mm	30.00
4	C-8.21-6Ø14	15	7.5	64	6xD14	8.21	D4.2@33 mm	30.00

### 3 RESULTS AND DISCUSSION

#### 3.1 Experimental Findings

After conducting the tensile experiments, different cracking formations and eventually cracking characteristics were noticed for each specimen. Figure 3 shows the state of each specimen after the end of the uniaxial tensile test. Cracks of various widths are obvious for the four specimens detailed with variable longitudinal reinforcement ratios. It is apparent that the final cracking formation differs between the specimens, depending on the longitudinal rebar percentage they are reinforced with.

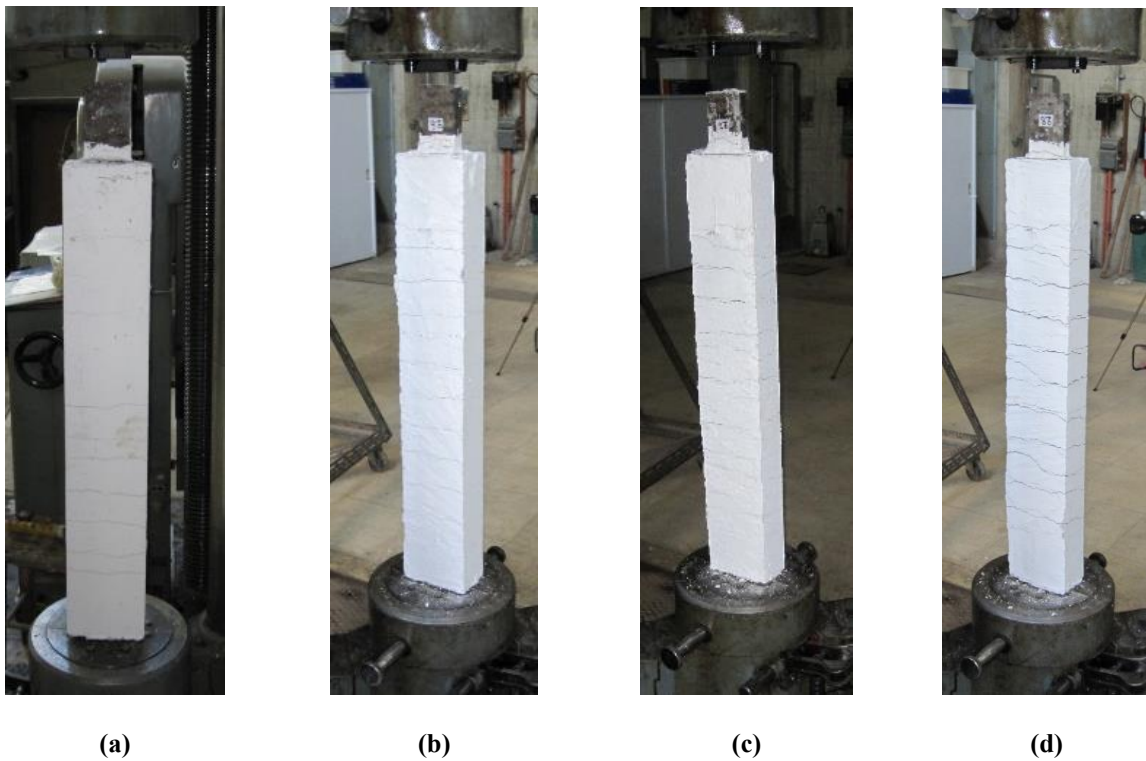


Figure 3: Specimens after the uniaxial tensile test: (a) C-5.47-4Ø14, (b) C-6.03-6Ø12, (c) C-7.15-4Ø16, (d) C-8.21-6Ø14.

#### 3.2 Analysis of experimental findings

The results of the analysis of the test findings for all segments are brought together in the following table and diagrams. Table 2 presents the width characteristics of the cracks. Figure

4 displays the variation of the crack width characteristics. Figure 5 – Figure 8 use column charts to display the results for the same type of cracking characteristics, e.g., maximum width, average width, etc.

Table 2: Crack width characteristics.

N/A	Specimen	Number of cracks [N]	Minimum crack width [ $W_{min}$ ] (mm)	Maximum crack width [ $W_{max}$ ] (mm)	Average crack width [ $W_{ave}$ ] (mm)	$W_{min}/W_{ave}$	$W_{max}/W_{ave}$	$W_{max}/W_{min}$
1	C-5.47-4 $\phi$ 14	12	0.5	1.5	1.125	0.44	1.33	3.00
2	C-6.03-6 $\phi$ 12	16	0.7	1.5	1.106	0.63	1.36	2.14
3	C-7.15-4 $\phi$ 16	13	0.6	2.3	1.485	0.40	1.55	3.83
4	C-8.21-6 $\phi$ 14	18	0.2	1.6	1.011	0.20	1.58	8.00

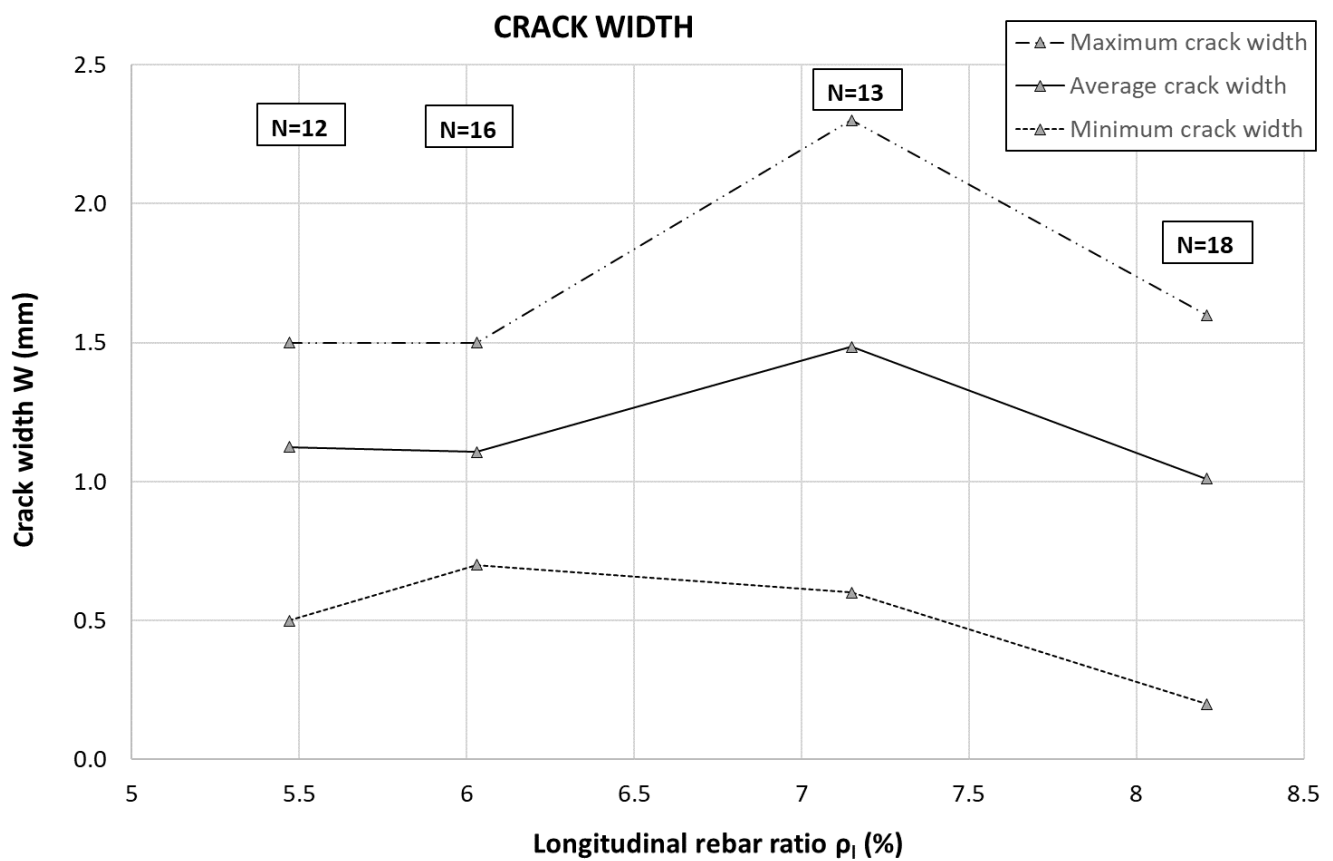


Figure 4: Variation of crack width relative to the longitudinal reinforcement ratio.

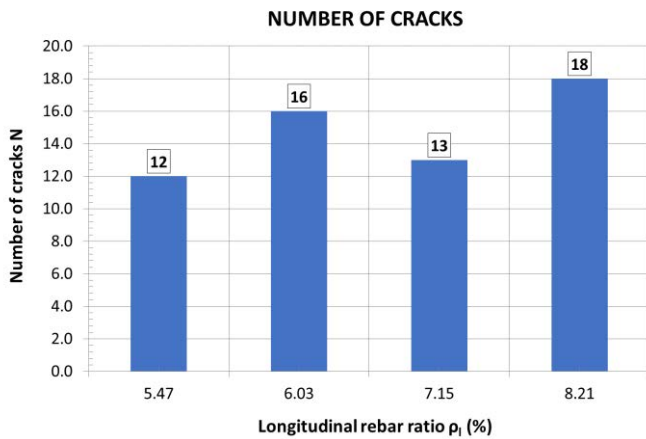


Figure 5: Column chart of number of cracks regarding the longitudinal rebar ratio.

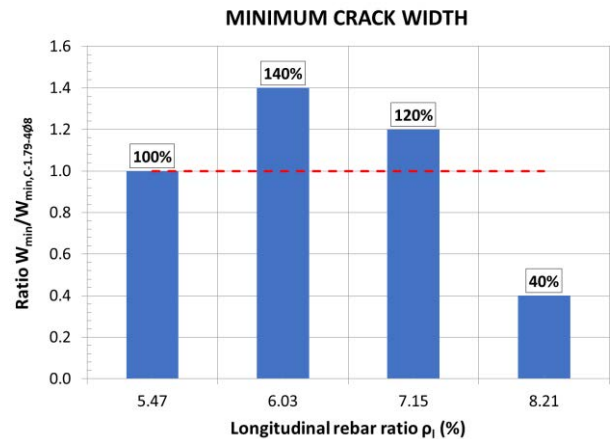


Figure 6: Column chart of minimum crack width as a percentage of the minimum crack width of the reference specimen.

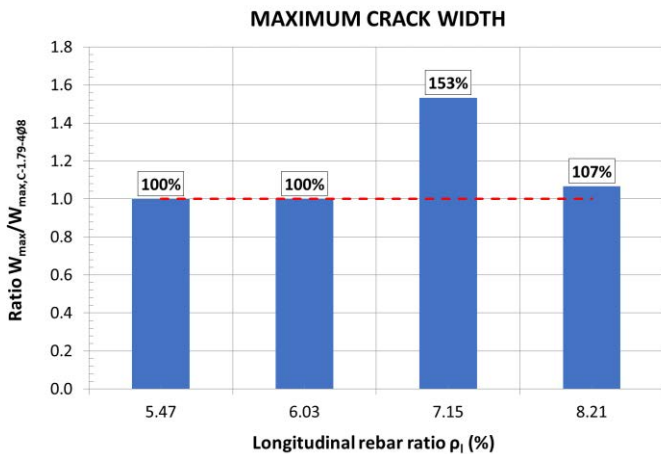


Figure 7: Column chart of maximum crack width as a percentage of the maximum crack width of the reference specimen.

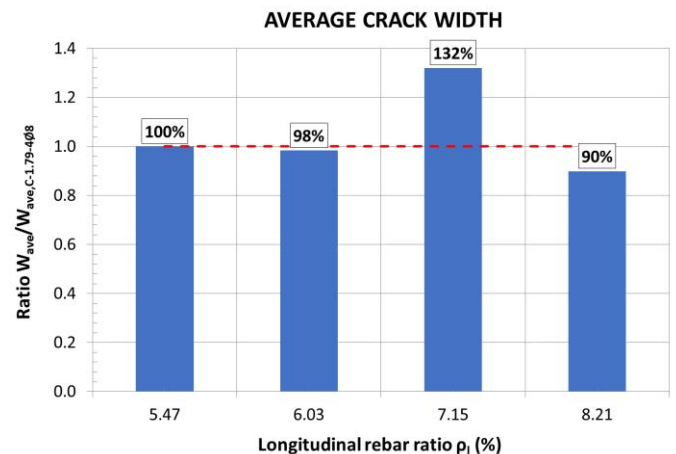


Figure 8: Column chart of average crack width as a percentage of the average crack width of the reference specimen.

The experimental findings of the test specimens were then analysed and evaluated:

1. Comparing the number of cracks formed according to the longitudinal rebar ratio each specimen is detailed with, it is obvious that the number of cracks formed increases with the increase of the longitudinal reinforcement ratio used but only when the number of rebars used remains the same; meaning either four or six rebars (Table 2, Figure 5). For a better understanding of this phenomenon, more experiments concerning different longitudinal reinforcement ratios and arrangements of rebars need to be performed.
2. Comparing the crack width with the rebar ratio used, it can be seen that there is not a definitive pattern which means that other times the width becomes smaller and other times the width becomes larger, whether that concerns the minimum, the maximum or the average width (Table 2, Figure 4).
3. The damage state of specimens indicates that cracks appear at or near to the tie positions (Figure 3). Thus, the presence of steel ties helps and promotes the disorganization of concrete around them.

## 4 CONCLUSIONS

This paper looks at four specimens to investigate cracking formation and behaviour in terms of crack characteristics for variable longitudinal reinforcement ratios. The following conclusions are drawn:

1. The degree of rebar ratio holds a significant part in terms of the formation of cracks and their characteristics, e.g., the number of cracks formed and the width of cracks.
2. Thus, the design of reinforced concrete structural components should take into account the ratio of longitudinal reinforcement because, as it is well known, large crack widths can lead to oxidization and deterioration of rebars and eventually affect structural safety.
3. The question arises whether, apart from the longitudinal ratio, the arrangement of rebars plays an essential role, too. Further research is needed on the subject using test specimens with different longitudinal reinforcement ratios and arrangements. This will help to check the impact that the mechanical factor of rebar arrangement has.

## REFERENCES

- [1] H. T. Hu and W. C. Schnobrich, "Nonlinear analysis of cracked reinforced concrete," *ACI Structural Journal*, vol. 87, no. 2, pp. 199–207, 1990.
- [2] Z. Shi, M. Suzuki, and M. Nakano, "Numerical Analysis of Multiple Discrete Cracks in Concrete Dams Using Extended Fictitious Crack Model," *Journal of Structural Engineering*, vol. 129, no. 3, pp. 324–336, 2003, doi: 10.1061/(asce)0733-9445(2003)129:3(324).
- [3] H. Mirzabozorg and M. Ghaemian, "Non-linear behavior of mass concrete in three-dimensional problems using a smeared crack approach," *Earthquake Engineering and Structural Dynamics*, vol. 34, no. 3, pp. 247–269, 2005, doi: 10.1002/eqe.423.
- [4] H. G. Sohn, Y. M. Lim, K. H. Yun, and G. H. Kim, "Monitoring crack changes in concrete structures," *Computer-Aided Civil and Infrastructure Engineering*, vol. 20, no. 1, pp. 52–61, 2005, doi: 10.1111/j.1467-8667.2005.00376.x.
- [5] M. M. Smadi and F. O. Slate, "Microcracking of high and normal strength concretes under short- and long-term loadings," *ACI Materials Journal*, vol. 86, no. 2, pp. 117–127, 1989.
- [6] D. S. Vijayan, L. R. Ayyasamy, A. S. Sharma, A. Mohan, P. Devarajan, and A. Sivasuriyan, "Finite element analysis of behavior and ultimate strength of composite column," *Science and Engineering of Composite Materials*, vol. 29, no. 1, pp. 176–182, 2022, doi: 10.1515/secm-2022-0017.
- [7] D. S. Vijayan *et al.*, "A Comprehensive Analysis of the Use of SFRC in Structures and Its Current State of Development in the Construction Industry," *Materials*, vol. 15, no. 19, 2022, doi: 10.3390/ma15197012.
- [8] T. Chrysanidis and V. Panoskaltsis, "Evaluation of cracking behavior of R/C vertical components reinforced with varying longitudinal reinforcement ratios," in *Proceedings of the XI International Conference on Structural Dynamics (EURODYN 2020)*, 2020, pp. 3186–3197. doi: 10.47964/1120.9260.18887.

- [9] T. Chrysanidis and V. Panoskaltsis, "Experimental investigation of the influence of tensile strain on the cracking of R/C vertical structural elements," in *Proceedings of the XI International Conference on Structural Dynamics (EURODYN 2020)*, 2020, pp. 3174–3185. doi: 10.47964/1120.9259.18582.
- [10] T. Chrysanidis and V. Panoskaltsis, "Does the degree of tensile strain have an impact on the cracking behavior of vertical structural elements?," in *IOP Conference Series: Materials Science and Engineering, 2020 5th International Conference on Civil Engineering and Materials Science (ICCEMS 2020)*, 2020, vol. 897. doi: 10.1088/1757-899X/897/1/012004.
- [11] I. Tegos, N. Giannakas, and T. Chrysanidis, "Serviceability cracking check of circular section piers," *Bridge Structures*, vol. 7, no. 1, pp. 43–52, 2011, doi: 10.3233/BRS-2011-018.
- [12] Wood Sharon, Wight James, and J. Moehle, "The 1985 Chile earthquake: Observations on earthquake-resistant construction in Vina del Mar," Urbana, Illinois, U.S., 1987.
- [13] M. Fintel, "Performance of Buildings With Shear Walls in Earthquakes of the Last Thirty Years," *PCI Journal*, vol. 40, no. 3. pp. 62–80, 2014. doi: 10.15554/pcij.05011995.62.80.
- [14] T. Chrysanidis and V. Panoskaltsis, "Analytical investigation of the tensile experiments modeling the elongation degree of R/C walls for studying the lateral buckling phenomenon," in *Proceedings of the 8th ECCOMAS Thematic Conference on Computational Methods in Structural Dynamics and Earthquake Engineering (COMPDYN 2021)*, 2021, pp. 2718–2729. doi: <https://doi.org/10.7712/120121.8669.18668>.
- [15] T. Chrysanidis and V. Panoskaltsis, "Analytical investigation of the tensile experiments to prisms with varying longitudinal ratio for studying the lateral buckling of R/C walls," in *Proceedings of the 8th ECCOMAS Thematic Conference on Computational Methods in Structural Dynamics and Earthquake Engineering (COMPDYN 2021)*, 2021, pp. 2730–2743. doi: <https://doi.org/10.7712/120121.8670.18669>.
- [16] T. Mitkou and T. Chrysanidis, "R/C column modeling using ANSYS and loading rate and mesh method influence studies," in *Proceedings of the 8th ECCOMAS Thematic Conference on Computational Methods in Structural Dynamics and Earthquake Engineering (COMPDYN 2021)*, 2021, pp. 1063–1084. doi: <https://doi.org/10.7712/120121.8546.19132>.
- [17] T. Chrysanidis and I. Tegos, "How does degree of elongation affect lateral buckling behavior of seismic walls?," *American Academic and Scholarly Research Journal*, vol. 7, no. 4, pp. 266–272, 2015.
- [18] N. Alamanis, "Influence of random soil strength properties on the earthquake vulnerability of slopes with embedded oil and natural gas pipelines," *Energy Systems*, 2020, doi: 10.1007/s12667-020-00394-9.
- [19] D. Parthiban *et al.*, "Role of industrial based precursors in the stabilization of weak soils with geopolymer – A review," *Case Studies in Construction Materials*, vol. 16, no. January, p. e00886, 2022, doi: 10.1016/j.cscm.2022.e00886.
- [20] S. S. Ali, N. Ijaz, N. Aman, A. Nasir, L. Anjum, and I. A. Randhawa, "Earth Sciences Pakistan (ESP)," *Earth Sciences Pakistan (ESP)1(2)*, vol. 1, no. 2, pp. 4–6, 2017.



- [21] N. Alamanis and P. Dakoulas, "Effects of spatial variability of soil properties and ground motion characteristics on permanent displacements of slopes," *Soil Dynamics and Earthquake Engineering*, vol. 161, no. June, p. 107386, 2022, doi: 10.1016/j.soildyn.2022.107386.
- [22] N. Alamanis and P. Dakoulas, "Simulation of random soil properties by the Local Average Subdivision method and engineering applications," *Energy Systems*, pp. 1–21, 2019, doi: 10.1007/s12667-019-00362-y.
- [23] P. Tselempi and T. Chrysanidis, "Differentiation of the construction cost of a fifteen-storey R/C building depending on the seismic hazard zone," in *Proceedings of the 8th ECCOMAS Thematic Conference on Computational Methods in Structural Dynamics and Earthquake Engineering (COMPDYN 2021)*, 2021, pp. 4520–4534. doi: <https://doi.org/10.7712/120121.8804.19133>.
- [24] T.-E. Makris and T. Chrysanidis, "Does the seismicity of the area have an impact on the construction cost of the load-bearing structure of R/C buildings?," in *Proceedings of the 8th ECCOMAS Thematic Conference on Computational Methods in Structural Dynamics and Earthquake Engineering (COMPDYN 2021)*, 2021, pp. 4535–4546. doi: <https://doi.org/10.7712/120121.8805.19134>.
- [25] Z. P. Bažant and B. H. Oh, "Spacing of Cracks in Reinforced Concrete," *Journal of Structural Engineering*, vol. 109, no. 9, pp. 2066–2085, 2008, doi: 10.1061/(asce)0733-9445(1983)109:9(2066).
- [26] B. H. Oh and S. H. Kim, "Advanced Crack Width Analysis of Reinforced Concrete Beams under Repeated Loads," *Journal of Structural Engineering*, vol. 133, no. 3, pp. 411–420, 2007, doi: 10.1061/(asce)0733-9445(2007)133:3(411).
- [27] T. Chrysanidis, "Influence of elongation degree on transverse buckling of confined boundary regions of R/C seismic walls," *Construction and Building Materials*, vol. 211, pp. 703–720, Jun. 2019, doi: 10.1016/J.CONBUILDMAT.2019.03.271.
- [28] T. Chrysanidis and I. Tegos, "Axial and transverse strengthening of R/C circular columns: Conventional and new type of steel and hybrid jackets using high-strength mortar," *Journal of Building Engineering*, vol. 30, no. January, p. 101236, 2020, doi: 10.1016/j.jobbe.2020.101236.
- [29] T. Chrysanidis, "Evaluation of Out-of-Plane Response of R/C Structural Wall Boundary Edges Detailed with Maximum Code-Prescribed Longitudinal Reinforcement Ratio," *International Journal of Concrete Structures and Materials*, vol. 14, no. 1. 2020. doi: 10.1186/s40069-019-0378-4.
- [30] T. Chrysanidis, "The effect of longitudinal reinforcement ratio on the lateral buckling behavior of R/C walls modelled using prism elements," *Journal of Building Engineering*, vol. 42, no. 102456, 2021, doi: 10.1016/j.jobbe.2021.102456.
- [31] H. M. Mohamed, H. M. Abdel-Baky, and R. Masmoudi, "Nonlinear stability analysis of concrete-filled fiberReinforced polymer-tube columns: Experimental and theoretical investigation," *ACI Structural Journal*, vol. 107, no. 6, pp. 699–708, 2010.
- [32] G. G. Penelis and A. J. Kappos, *Earthquake-resistant Concrete Structures*. London, UK: E & F N SPON (Chapman & Hall), 1996.
- [33] G. Penelis, K. Stylianidis, A. Kappos, and C. Ignatakis, *Reinforced Concrete Structures*. Thessaloniki, Greece: A.U.Th. Press, 1995.

- [34] Standards New Zealand, “NZS 3101:2006, Concrete structures standard: Part 1 – The design of concrete structures,” Wellington, New Zealand, 2006.
- [35] Canadian Standards Association, “CAN/CSA-A23.3-04, Design of Concrete Structures (Update No. 2 - July 2007),” Mississauga, Ontario, Canada, 2007.
- [36] European Committee for Standardization, “EN 1998-1:2004, Eurocode 8: Design of structures for earthquake resistance - Part 1: General rules, seismic actions and rules for buildings,” Brussels, Belgium, 2004.
- [37] Ministry of Environment Planning and Public Works, “Greek Code for the Design and Construction of Concrete Works,” Athens, Greece, 2000, p. . (In Greek).
- [38] International Conference of Building Officials, “Uniform Building Code – Volume 2: Structural Engineering Design Provisions,” Whittier, California, USA, 1997.